

Multivariate Calibration and Experimental Validation of a 3D Finite Element Thermal Model for Laser Powder-Bed Fusion Metal Additive Manufacturing

M. Mahmoudi^a, G. Tapia^a, K. Karayagiz^b, B. Franco^b, J. Ma^b, R. Arroyave^b, I. Karaman^b, A. Elwany^{a,*}

^aDepartment of Industrial & Systems Engineering, Texas A&M University, College Station, TX

^bDepartment of Materials Science & Engineering, Texas A&M University, College Station, TX

Abstract

Metal additive manufacturing (AM) typically suffers from high degree of variability in the properties/performance of the fabricated parts, particularly due to the lack of understanding and control over the physical mechanisms that govern microstructure formation during fabrication. This paper directly addresses an important problem in AM: the determination of the thermal history of the deposited material. Any attempts to link process to microstructure in AM would need to consider the thermal history of the material. In-situ monitoring only provides partial information and simulations may be necessary to have a comprehensive understanding of the thermo-physical conditions to which the deposited material is subjected. We address this in the present work through linking thermal models to experiments via a computationally efficient surrogate modeling approach based on multivariate Gaussian processes (MVGPs). The MVGPs are then used to calibrate the free parameters of the multi-physics models against experiments, sidestepping the use of prohibitively expensive Monte Carlo-based calibration. This framework thus makes it possible to efficiently evaluate the impact of varying process parameter inputs on the characteristics of the melt pool during AM. We demonstrate the framework on the calibration of a thermal model for Laser-Powder Bed Fusion AM of Ti-6Al-4V against experiments carried out over a wide window in the process parameter space. While this work deals with problems related to AM, its applicability is wider as the proposed framework could potentially be used in many other ICME-based problems where it is essential to link expensive computational materials science models to available experimental data.

Keywords: Metal Additive Manufacturing, Powder Bed Fusion, Ti-6-Al-4V, Finite Element Thermal Models, Uncertainty Quantification

1. Introduction

Integrated Computational Materials Engineering (ICME) prescribes a framework for the acceleration in the development and deployment of materials through the establishment and exploitation of process-structure-property-performance (PSPP) relationships. PSPPs in turn can be established through linking materials models at multiple length (and possibly time) scales. The goal in ICME is to optimize the materials, manufacturing process, and component designs prior to part fabrication [1]. Inherently, ICME involves utilization of physics-based simulation models that help understand the behavior of complex systems. These models use the system governing equations to compute and predict specific quantities of interest (QoIs). As a well-established fact, all of these simulation models are imperfect and thus their predictions will differ

from the actual physical phenomena they are trying to describe.

The disagreement between the real-world and the model outputs can be attributed to one or more of the following factors: (1) incomplete understanding of the physical system, (2) incomplete information about model parameters, (3) incorrect values for the model inputs, (4) natural stochastic behavior of the system, and (5) uncertainties associated with available numerical simulation algorithms [1–5]. Hence, identification, characterization, and quantification of the uncertainties associated with these models become necessary in order to strengthen the robustness of model predictions, which is in turn essential if one is to use the models to guide the design/optimization of the systems (in this case, materials).

As an independent field of study, Uncertainty Quantification (UQ) seeks to address the challenges associated with the (unknown) uncertainties in models used to describe the behavior of complex systems. UQ is an established field that has been successfully applied to many areas including climate models [6], computational fluid dynamics [7], forestry [8], nuclear engineering [9], and econometrics [10]. Although UQ is a

*Corresponding author

Email addresses: mahmoudi@tamu.edu (M. Mahmoudi), gustavo@tamu.edu (G. Tapia), kubra87@tamu.edu (K. Karayagiz), be.franco@tamu.edu (B. Franco), jm@tamu.edu (J. Ma), rarrayave@tamu.edu (R. Arroyave), ikaraman@tamu.edu (I. Karaman), elwany@tamu.edu (A. Elwany)

key need for computational materials models [11, 12], there is a literature gap in this area [13]. Chernatynskiy et al. [3] present a review of the few existing works on UQ of multi-scale simulation models. More recently, Tapia et al. [13] conduct UQ for a physics-based precipitation model of nickel-titanium shape memory alloys through combining experimental and computer simulation data.

Additive Manufacturing (AM) is an area that can potentially benefit substantially from the ICME framework. First, AM processes such as Laser Powder-Bed Fusion (L-PBF) are recognized for the high variability in the performance, composition, and microstructure of parts [14]. This variability is due to our incomplete understanding of the many complex and coupled phenomena that occur as energy interacts with raw material to produce a solid part [15]. Currently, many researchers work on developing simulation models at different scales to help understand different aspects of a specific AM process. For example for the L-PBF process, different simulation models exist that focus on different physical aspects, including characteristics of the powder-bed, evolution of the melt pool, solidification process, and generation of residual stresses, etc. Inevitably, these models introduce various sources of uncertainty [16]. Second, ICME provides the necessary infrastructure to support and accelerate the qualification and certification [17], a key technological barrier of AM. Recently, Hu and Mahadevan [18, 19] discussed the opportunities and challenges of how state-of-the-art UQ techniques can be used for predicting materials properties in AM processes.

The purpose of this work is to conduct formal UQ for a computational materials model used to predict melt pool characteristics in L-PBF metal AM processes. More specifically, we perform statistical calibration of an FEM based thermal model via surrogate (or reduced order) modeling and Bayesian inference. The statistical calibration problem (also known as the inverse UQ problem) refers to making inference on the posterior distributions of a set of calibration parameters such that model predictions are in agreement with experimental observations [20]. To the best of the authors' knowledge, the current work is the first to conduct such rigorous calibration using a multivariate Gaussian Process-based (GP) surrogate model. While the focus of the work is on specific physical phenomena associated with L-PBF AM, the overall framework can be readily adapted to address similar problems that involve systematic calibration of complex multiple-output computational materials models.

Prior to this work, UQ of ICME simulation models has been classically conducted using Monte Carlo methods (see [21–25]). However, for many computationally expensive models, Monte Carlo methods are impractical, and sometimes even unfeasible, as they require sufficiently large numbers of simulation runs in order to acquire the statistics necessary to adequately

characterize model uncertainty. This is especially true in the specific case of computational models for AM that tend to be computationally demanding, which precludes the utilization of Monte Carlo methods. To address this, we construct a surrogate model (also known as an emulator or meta-model). This represents a statistical approximation that can be used in lieu of the original computationally expensive simulation model without sacrificing too much accuracy. Although surrogate modeling has been studied in prior works, one important distinguishing feature of the surrogate model developed in the present study is its ability of approximating simulation models that have multiple outputs or QoIs. This is an important feature since multi-output simulation models are quite common in science and engineering applications [26, 27]. Conventional UQ approaches for multi-output models typically ignore correlations that might exist among model outputs, and thus usually conduct independent UQ analysis for each output independently. Clearly, this de-coupling overlooks inherent coupling or interdependence that may exist among multiple outputs of a single model.

The remainder of this paper is organized as follows: Section 2 has two subsections: Section 2.1 introduces the FEM based simulation model used in this work. Section 2.2 describes the statistical framework used for building the surrogate and calibration models. Section 3 reports the results of implementing the proposed calibration procedure for the melt pool FEM based simulation model using both simulations and experimental characterization. Section 4 concludes the paper with a summary of findings and directions for future research.

2. Proposed Framework

This section will start by presenting the physics-based FEM based thermal model, followed by the multivariate statistical framework used to calibrate that model. Readers who are not focused on understanding the details of mathematical and statistical model developments can skip Section 2.2 and proceed directly to the results and discussion in Section 3.

2.1. Melt pool Modeling through FEM based thermal modeling

L-PBF processes offer attractive advantages and capabilities over conventional manufacturing techniques. These include, for example, higher geometric freedom, flexibility to customize parts, and recently the potential capability of tailoring the microstructures (and hence the properties) of fabricated parts. However, they are in the meantime very complex processes that involve several physical mechanisms most of which are not yet fully understood. Therefore, it is crucial to develop better understanding of these mechanisms that drive the thermal history within the part during fabrication. Ideally, in-situ thermal monitoring can be used to

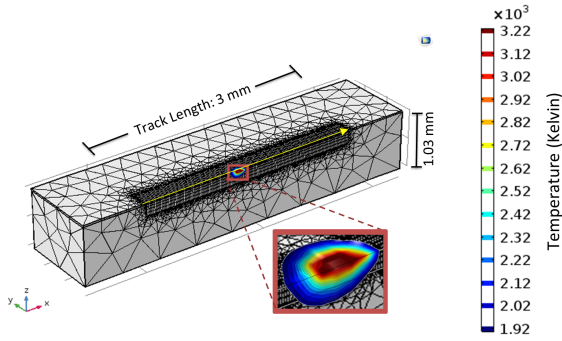


Figure 1: Sample output of the melt pool model for Ti-6Al-4V powder on a Ti-6Al-4V substrate, showing the melt pool temperature profiles in three-dimensions

capture information about thermal histories during fabrication. However, experimental measurement of the thermal field in L-PBF is extremely difficult due to a number of challenges such as very high thermal gradients and cooling rates, micro-scale melt pool size, and emissivity variations, among many other challenges. Consequently, numerical methods are needed to complement experiments in understanding the thermal history during the fabrication of L-PBF parts.

Formally, we define the melt pool as the region in the laser-powder interface at which metal powder particles fuse to form a pool of molten metal that eventually solidifies after the laser beam moves to another location. In this paper, we developed a three-dimensional FEM based thermal model implemented in COMSOL Multiphysics software to study melt pool characteristics, including geometry and thermal profiles, during the fabrication of single tracks printed in a thin layer of powder on top of a solid substrate. The powder layer was assumed as a $30\ \mu\text{m}$ continuum medium over a 1 mm thick substrate. Ti-6Al-4V alloy was selected as the material for both the powder layer and the substrate. To ensure accurate analysis, a fine mesh element was used for the laser-powder interaction zones, while a coarser element was employed for the rest of the simulation domain. Second-order quadrilateral Lagrange elements were used for the entire domain, while the $30\ \mu\text{m}$ fine elements were found suitable for the powder-bed based on the mesh convergence analysis. Single track simulations were run for a 3 mm-long track. Figure 1 shows a sample output of the model with melt pool temperature profiles.

An appreciable number of FEM based thermal models have been developed to predict the thermal history and melt pool geometry during L-PBF. In these works, the effects of process parameters (e.g., laser power, scanning velocity, hatch spacing), material properties, and powder properties (e.g., particle size distribution, layer thickness) have been investigated. For these melt pool models, an appropriate powder-bed model should be employed. Modeling of the powder-bed has been done in two different ways: powder-scale (refer to [28–

35]) and continuum-scale (refer to [36–43]). Although the first approach enables simulating the size variations and the local changes in the melt pool such as incomplete melting or formation of pores [28, 29], it is computationally expensive such that it is almost impossible to use it for full-part simulation. The latter approach, on the other hand, has been widely employed due to its relatively low computational cost and ease of implementation. While some studies have taken fluid dynamics effects in the melt pool into account (e.g., Marangoni convection in [33, 44, 45]), a significant number of works in the literature have neglected those effects to simplify the model (see for example [38–40, 43]). The change in volume during melting of the powder [42, 46, 47] and layer built-up were modeled in some studies [37, 41, 48, 49]. We refer the interested readers to review papers on numerical modeling and simulation of AM for more information [50–52].

The model used in this work accounts for several heat transfer mechanisms that take place during metal L-PBF. In particular, conduction, convection, radiation, phase transitions (namely, solid-to-liquid and liquid-to-gas transitions), latent heat of melting/evaporation, temperature dependent material properties, and the effective thermo-physical properties for the powder layer were considered. Furthermore, heat loss due to evaporation was incorporated by employing a simple approach based on the implementation of a heat sink on the powder surface. The laser beam was defined as a two-dimensional Gaussian distributed moving heat source. The initial temperature of the build was set to the ambient temperature (298 K). Natural convection, radiation and evaporation were employed as boundary conditions on the powder surface, while a symmetry boundary condition was applied along the scanning path to reduce the computational cost. All other boundaries were maintained at the ambient temperature.

Since the thermal model takes different physical mechanisms into account, there are multiple materials parameters that influence the model results, and thus, the predictive capabilities of the model. After preliminary simulation experiments, the following parameters were identified as most significant on variability in model outputs: (1) laser absorptivity, (2) powder-bed porosity, and (3) thermal conductivity of the liquid. It is known that the laser absorptivity is a function of temperature and has different values for powder, solid and liquid materials. There are several factors (e.g., beam intensity, wavelength, temperature, oxidation, powder size and distribution) affecting the absorptivity of the material. Therefore, it is difficult to experimentally measure it. Note that while low values of absorptivity result in insufficient energy input and incomplete melting of the powder particles, very high values lead to overheating of the particles, hence, over estimation of the melt pool size.

Moreover, to account for the effect of Marangoni

convection on the melt pool size and geometry, the thermal conductivity of liquid was increased according to [39, 53, 54]. However, there is no consensus in the community on the level of this increase. Powder porosity is used as an input to predict the effective thermo-physical properties (thermal conductivity, density, heat capacity) of the powder layer. Therefore, it has a significant influence on the predicted thermal distribution. Considering the aforementioned aspects, a need for the calibration of these three parameters was realized.

2.2. Multivariate statistical calibration

After describing the melt pool FEM based simulation model in Section 2.1, we now describe in details the multivariate statistical framework that will be employed to calibrate that model. This approach is referred to as *calibration of computer models* by Kennedy and O’Hagan [55]. We emphasize that although AM is our focus application platform, the framework developed in this section can be readily generalized to other problems.

Before we introduce the mathematical formulations, we establish notation and some definitions. Since the word *model* will be employed to refer to different types of models that constitute the building blocks of the framework, we clearly define specific cases to avoid misinterpretation and ambiguity. We use *computer model* to denote a computational model implemented via a computer code that simulates and recreates any process (physical, social, mathematical, etc.) by a set of calculations derived from proper study of the process. One example of a computer model is the thermal model explained in Section 2.1. The term *statistical model* will refer to the calibration methodology presented in this section, and is sub-divided in two key components: the *surrogate model* and the *calibration model*, which will be defined in the following paragraphs.

Previous approaches for the calibration of computer models using rigorous statistics rely on Monte Carlo (MC) methods. While MC methods are extremely valuable and well-studied, the fact that they necessitate generating sufficiently large numbers of simulations (sometimes in the order of 15,000 - 20,000 simulations) makes them impractical for calibrating computationally expensive models. One possible approach to overcome this challenge is using a two-stage approach based on surrogate modeling (also called meta-modeling or emulation) and suggested in a series of works [55–58]. The *surrogate model* is thus the computationally efficient statistical approximation of the original computer model.

In the calibration problem, whether or not a surrogate model is used, we distinguish between two different types of inputs to the computer model [13]:

- *Control inputs* (denoted by \mathbf{x}) are inputs to the computer model that are directly set to known

pre-determined values by the user. Examples of control inputs in some computer models include temperature, pressure, or velocity.

- *Calibration parameters* (denoted by θ) are inputs or parameters to the computer model that are unknown with certainty, or not measurable, at the time of simulation, but do influence the results of the computations. Examples include material properties or unknown physical constants.

The goal of the *calibration model* is thus to estimate the calibration parameters such that the computer model simulations agree with experimental observations of the real process being simulated [13]. In mathematical notation, the statistical model follows the equation:

$$\mathbf{y}^E(\mathbf{x}) = \mathbf{y}^S(\mathbf{x}, \theta^*) + \delta(\mathbf{x}) + \epsilon(\mathbf{x}) \quad (1)$$

where the experimental observation \mathbf{y}^E of the real process run at some values of control inputs \mathbf{x} is equal to the summation of the response of the computer model \mathbf{y}^S , a discrepancy (or inadequacy) function δ , and some measurement error ϵ , and the objective is to estimate the values of the calibration parameters θ^* . Detailed definitions for each term in Equation (1) will be provided as we describe the two stages of the statistical model in the following subsections.

2.2.1. Multivariate Surrogate Model

In this section, we build a multivariate surrogate model that replaces the computer model $\mathbf{y}^S(\mathbf{x}, \theta)$ in Equation (1). For detailed derivations, the interested reader is encouraged to study the work by Conti and O’Hagan [59]. Note that, we define the computer model as a function $\mathbf{y}^S = f(\cdot)$ that takes as input the control inputs \mathbf{x} and the calibration parameters θ , and returns a q -dimensional response vector $\mathbf{y}^S \in \mathbb{R}^q$. The inputs \mathbf{x} and parameters θ lie in some multidimensional spaces $\mathcal{X} \subseteq \mathbb{R}^p$ and $\mathcal{T} \subseteq \mathbb{R}^t$, respectively. Thus, the computer model f is essentially a mapping $f : \mathcal{X} \times \mathcal{T} \mapsto \mathbb{R}^q$. Although f is a deterministic function (that is, if run multiple times at same input values, it will return the same value for responses), in order to approximate it with a surrogate model, we can regard f as an stochastic process [59].

As mentioned in Section 1, we employ GP models that are known for their attractive mathematical and computational properties [60]. In the simple univariate case, a GP model is a non-parametric statistical model in which a stochastic process $f(\cdot)$ is assumed to have all of its finite-dimensional distributions as multivariate normal [61]. Therefore, the joint probability distribution of the outputs from the stochastic process at any finite set of inputs $\{\mathbf{x}_1, \dots, \mathbf{x}_n\}$ (assuming f only takes \mathbf{x} as inputs for now) is modeled as an n -dimensional multivariate normal distribution

$$p(f(\mathbf{x}_1), \dots, f(\mathbf{x}_n) | \Phi) \sim \mathcal{M}\mathcal{V}\mathcal{N}_n(\mathbf{m}, \mathbf{C})$$

where the mean vector \mathbf{m} is defined by a mean function $m(\cdot)$, and covariance matrix \mathbf{C} is defined by a covariance function $c(\cdot, \cdot)$, with $\mathbb{E}[f(\mathbf{x})|\Phi] = m(\mathbf{x})$ and $\text{cov}[f(\mathbf{x}_i), f(\mathbf{x}_j)|\Phi] = c(\mathbf{x}_i, \mathbf{x}_j)$. The whole distribution is fully defined by some set of hyperparameters Φ . Hence, we denote a univariate GP by

$$f(\cdot) | \Phi \sim \text{GP}(m(\cdot), c(\cdot, \cdot))$$

Now, generalizing the univariate formulation to a multivariate case, the joint probability distribution follows a *matrix-variate* normal distribution

$$p(f(\mathbf{x}_1), \dots, f(\mathbf{x}_n) | \Phi) \sim \mathcal{MVN}_{n,q}(\mathbf{m}, \mathbf{C}) \quad (2)$$

with *mean matrix* \mathbf{m} and *cross-covariance matrix* \mathbf{C} , and fully defined by some set of hyperparameters Φ . The multivariate q -dimensional GP is denoted as

$$f(\cdot) | \Phi \sim \mathcal{GP}_q(m(\cdot), c(\cdot, \cdot), \Sigma) \quad (3)$$

where $c(\cdot, \cdot)$ is a positive definite correlation function accounting for correlation in the input space with $c(\mathbf{x}, \mathbf{x}) = 1$, and $\Sigma \in \mathbb{R}_+^{q,q}$ is a positive definite matrix accounting for correlations between outputs. After this brief digression to set notation, we translate all these definitions into our original context, $\mathbf{y}^S = f(\mathbf{x}, \theta)$. We build a multivariate GP-based on Equation (3), with the i -th input tuple denoted as $(\mathbf{x}, \theta)_i = [x_{i,1}, \dots, x_{i,p}, \theta_{i,1}, \dots, \theta_{i,t}]^\top$. Mean and correlation functions are defined as follows:

$$m(\mathbf{x}, \theta) = \mathbf{B}^\top h(\mathbf{x}, \theta) \quad (4)$$

$$c((\mathbf{x}, \theta)_i, (\mathbf{x}, \theta)_j) = \exp\left[-((\mathbf{x}, \theta)_i - (\mathbf{x}, \theta)_j)^\top R((\mathbf{x}, \theta)_i - (\mathbf{x}, \theta)_j)\right] \quad (5)$$

where $h : \mathcal{X} \times \mathcal{T} \rightarrow \mathbb{R}^m$ is a function (defined by the modeler) that maps the input space to m basis functions, $\mathbf{B} = [\beta_1, \dots, \beta_q] \in \mathbb{R}^{m,q}$ is a matrix of regression coefficients, and $R = \text{diag}(\mathbf{r})$ is a diagonal matrix of positive roughness parameters with $\mathbf{r} = [r_1, \dots, r_p, r_{p+1}, \dots, r_{p+t}] \in \mathbb{R}_+^{p+t}$. The roughness parameter vector \mathbf{r} explains how rough (or smooth) the function is, i.e. how quickly its values change across the input domain.

With the choices of linear regression mean function in Equation (4), stationary squared exponential correlation function in Equation (5), and separable covariance structure (with $\Sigma \in \mathbb{R}_+^{q,q}$ accounting for correlations between outputs), the model is fully defined by

$$\Phi_{\text{sim}} = \{\mathbf{B}, \Sigma, \mathbf{r}\} \quad (6)$$

Under these settings, we run the computer model for several simulations to gather a set of data that will be used to train and build the surrogate model. There are different approaches to optimally select the points at which these simulations will be run to generate the

training data set (given the computational burden of the computer model). However, we choose to employ the Latin Hypercube Sampling (LHS) method given its ability to explore the input space uniformly and homogeneously. The training data set consists of N points and is denoted by

$$\mathbf{X}^S = \begin{bmatrix} (\mathbf{x}, \theta)_1 \\ \vdots \\ (\mathbf{x}, \theta)_N \end{bmatrix} \in \mathbb{R}^{N,p+t}$$

and

$$\mathbf{Y}^S = \begin{bmatrix} \mathbf{y}^S(\mathbf{x}, \theta)_1 \\ \vdots \\ \mathbf{y}^S(\mathbf{x}, \theta)_N \end{bmatrix} \in \mathbb{R}^{N,q}$$

where \mathbf{X}^S is an $N \times (p+t)$ input matrix and \mathbf{Y}^S is an $N \times q$ output matrix. It can then be shown, as presented in Conti and O'Hagan [59], that the conditional posterior distribution of f given \mathbf{r} , after integrating out \mathbf{B} and Σ , is a multivariate q -dimensional T Process, such that the probability distribution it yields is a matrix-variate T distribution:

$$f(\cdot) | \mathbf{X}^S, \mathbf{Y}^S, \mathbf{r} \sim \mathcal{TP}_q(m^*(\cdot), c^*(\cdot, \cdot), \hat{\Sigma}, N-m) \quad (7)$$

with $N-m$ degrees of freedom (denoted as *dof* henceforth), and

$$m^*(\mathbf{x}, \theta) = \hat{\mathbf{B}}^\top h(\mathbf{x}, \theta) + (\mathbf{Y}^S - \mathbf{H}\hat{\mathbf{B}})^\top \mathbf{A}^{-1} \mathbf{t}(\mathbf{x}, \theta) \quad (8)$$

$$c^*((\mathbf{x}, \theta)_i, (\mathbf{x}, \theta)_j) = c((\mathbf{x}, \theta)_i, (\mathbf{x}, \theta)_j) - \mathbf{t}^\top(\mathbf{x}, \theta)_i \mathbf{A}^{-1} \mathbf{t}(\mathbf{x}, \theta)_j + [h(\mathbf{x}, \theta)_i - \mathbf{H}^\top \mathbf{A}^{-1} \mathbf{t}(\mathbf{x}, \theta)_i]^\top \times (\mathbf{H}^\top \mathbf{A}^{-1} \mathbf{H})^{-1} \times [h(\mathbf{x}, \theta)_j - \mathbf{H}^\top \mathbf{A}^{-1} \mathbf{t}(\mathbf{x}, \theta)_j] \quad (9)$$

where

$$\mathbf{H}^\top = [h(\mathbf{x}, \theta)_1, \dots, h(\mathbf{x}, \theta)_N] \in \mathbb{R}^{m,N}$$

$$\mathbf{A} = [c((\mathbf{x}, \theta)_i, (\mathbf{x}, \theta)_j)]_{i,j=1:N} \in \mathbb{R}_+^{N,N}$$

$$\mathbf{t}^\top(\mathbf{x}, \theta)_i = [c((\mathbf{x}, \theta)_i, (\mathbf{x}, \theta)_1), \dots,$$

$$c((\mathbf{x}, \theta)_i, (\mathbf{x}, \theta)_N)] \in \mathbb{R}^N$$

$$\hat{\mathbf{B}} = (\mathbf{H}^\top \mathbf{A}^{-1} \mathbf{H})^{-1} \mathbf{H}^\top \mathbf{A}^{-1} \mathbf{Y}^S$$

$$\hat{\Sigma} = (N-m)^{-1} (\mathbf{Y}^S - \mathbf{H}\hat{\mathbf{B}})^\top \mathbf{A}^{-1} (\mathbf{Y}^S - \mathbf{H}\hat{\mathbf{B}})$$

To summarize, the T process defined in Equations (7)-(9) can be used as a fast surrogate model for the simulation model. Its mean function m^* interpolates the training data $(\mathbf{X}^S, \mathbf{Y}^S)$ exactly and provides an approximation to $f(\cdot)$. For the surrogate model to be only dependent on the data, we need to integrate

out the roughness parameters \mathbf{r} . This step is achieved through a Bayesian approach, for which the posterior distribution of the roughness parameters (again after proper integration of \mathbf{B} and Σ , see [59]) is given by:

$$\pi(\mathbf{r} | \mathbf{X}^S, \mathbf{Y}^S) \propto \pi(\mathbf{r}) |\mathbf{A}|^{-\frac{q}{2}} |\mathbf{H}^\top \mathbf{A}^{-1} \mathbf{H}|^{-\frac{q}{2}} |\mathbf{Y}^{S^\top} \mathbf{G} \mathbf{Y}^S|^{-\frac{N-m}{2}}, \quad (10)$$

with

$$\mathbf{G} = \mathbf{A}^{-1} - \mathbf{A}^{-1} \mathbf{H} (\mathbf{H}^\top \mathbf{A}^{-1} \mathbf{H})^{-1} \mathbf{H}^\top \mathbf{A}^{-1}.$$

Subsequently, we set the prior distribution for \mathbf{r} to follow a joint log-logistic distribution as below:

$$\pi(\mathbf{r}) = \prod_{i=1}^{p+t} (1 + r_i^2)^{-1}. \quad (11)$$

We estimate posterior distributions of these roughness parameters using the *Metropolis Hastings* algorithm and select their mode as the values to be used in the surrogate model defined in Equations (7), (8) and (9). Once the roughness parameters \mathbf{r} have been estimated, the surrogate model in Equation (7) is fully defined. At this point, we assess its performance through *k-fold cross validation* (CV). CV is a common technique to evaluate the adequacy of predictive models, including surrogate models, through computing a metric that captures the deviation of the predictions obtained using the predictive model (the surrogate model in our case) and the true quantity being predicted (computer model predictions in our case). Put simply, our target to ensure that predictions obtained using the surrogate model are close to those obtained using the original computer model. In a CV procedure, we partition the training dataset $(\mathbf{X}^S, \mathbf{Y}^S)$ into k disjoint partitions. $k - 1$ of these partitions are used to train the surrogate model, and then predictions are made on the left-out partition using Equation (8). These predictions are then compared with the computer model predictions. This process is iterated k times, such that at every iteration, a different partition is left out, and after all k iterations all partitions have been left out once and only once. Finally, the performance metric is computed. Many metrics have been reported in the literature on predictive modeling and machine learning. We utilize the well-known *mean absolute percentage error* (MAPE) defined as

$$\text{MAPE}_j = \frac{1}{N} \sum_{i=1}^N |y_{i,j}^S - \hat{y}_{i,j}^S| \quad \forall j \in \{1, \dots, q\},$$

where $y_{i,j}^S$ is j -th element of the computer model output at input $(\mathbf{x}, \boldsymbol{\theta})_i$, and $\hat{y}_{i,j}^S$ is the j -th element of the surrogate model prediction evaluated at the same input $(\mathbf{x}, \boldsymbol{\theta})_i$ using the estimated values for \mathbf{r} .

If CV results are satisfactory (i.e. MAPE is low), then we can move to the next step of the calibration procedure in Section 2.2.2. Otherwise, we seek to improve the predictive power of the surrogate model.

More specifically, we run an additional number of computer model simulations, such that we have a larger training data set that results in a better surrogate model. We achieve this through an *adaptive sampling* (AS) technique to select new data points to sample based on present results. The algorithm devised for this purpose is similar to a *grid search*, where we subdivide each dimension from the $(p + t)$ -dimensional input spatial domain into grids (perhaps with different number of divisions per dimension) yielding N_{AS} number of different data points within the grid,

$$\mathbf{X}^{\text{grid}} = \begin{bmatrix} (\mathbf{x}, \boldsymbol{\theta})_1^{\text{grid}} \\ \vdots \\ (\mathbf{x}, \boldsymbol{\theta})_{N_{\text{AS}}}^{\text{grid}} \end{bmatrix} \in \mathbb{R}^{N_{\text{AS}} \cdot (p+t)}$$

and calculate the predictive variance for each point based on the probability distribution from Equation (7):

$$\text{AS} = \left[\frac{1}{q} \sum_{j=1}^q c^* \left((\mathbf{x}, \boldsymbol{\theta})_i^{\text{grid}}, (\mathbf{x}, \boldsymbol{\theta})_i^{\text{grid}} \right) \hat{\Sigma}_{j,j} \right]_{i=1:N_{\text{AS}}} \in \mathbb{R}_+^{N_{\text{AS}}}$$

where $\hat{\Sigma}_{j,j}$ is the j -th element in the diagonal of matrix $\hat{\Sigma}$.

Elements of the vector AS represent the average predictive variance among all outputs at a specific input point. The vector is then sorted in descending order, and the corresponding points for the first 20 elements (with largest average predictive variance) are selected to be evaluated using the expensive computer model. The underlying hypothesis is that adding these points that showed high predictive variance to the training data set \mathbf{X}^S will improve the predictive power of the surrogate model. We denote the set with these new appended data points by \mathbf{X}^{AS} .

In implementing the adaptive sampling procedure as outlined above, we include two filters that ensure better sampling of new points. The first filter flags points that are very close to one other. This filter essentially avoids sampling more than one point from within a small sub-set of the input space, since this is not likely to provide more information. The filter takes the first 20 elements of the vector AS with largest predictive variance, and selects those that are at least some distance threshold τ_{AS} apart from one another. When a point is flagged and excluded, the next point from vector AS becomes a candidate to be added to \mathbf{X}^{AS} if it satisfies the filter criterion.

The second filter for the AS algorithm addresses the issue of extrapolation. It is well-known that GP predictive models have less predictive power at regions outside the domain of the training set \mathbf{X}^S . Hence, this filter excludes points within vector AS that are located outside of that domain. It is important to point out that if the initial selection of design points in the data set \mathbf{X}^S uniformly covers the input space (as is the case with

Latin Hypercube Design), then this second filter will not be employed too often.

The AS algorithm can be iteratively conducted until a satisfactory value of the cross validation predictive error, MAPE, set by the user is achieved.

2.2.2. Multivariate Calibration Model

Once the surrogate model has been adequately constructed, it can now be used in lieu of the original computer model in Equation (1) to generate sufficiently large number of simulations needed to conduct calibration of the parameters θ . Some of the steps in developing the following calibration procedure follow the work of Bhat et al. [62].

We start by elucidating the two remaining terms of the statistical model given in Equation (1). The term $\delta(\mathbf{x})$ is a discrepancy or model inadequacy function. This function accounts for factors that result in deviation between the computer model predictions and the real process being simulated, including missing physics, simplifying assumptions, and numerical errors. The term $\epsilon(\mathbf{x})$ models the measurement error associated with experimental observations. Note that both of these terms depend only on control inputs \mathbf{x} , since the calibration parameters are not changed or controlled in experiments.

Similar to what was done with the surrogate model in Section 2.2.1, we model $\delta(\cdot)$ as a multivariate q -dimensional GP,

$$\delta(\cdot) \mid \mathbf{r}_\delta, \sigma_\delta \sim \mathcal{GP}_q(\mathbf{0}, c_\delta(\cdot, \cdot) \Sigma_\delta) \quad (12)$$

with mean function that is equal to 0 for all elements, and a stationary squared exponential correlation function

$$c_\delta(\mathbf{x}_i, \mathbf{x}_j) = \exp\left[-(\mathbf{x}_i - \mathbf{x}_j)^\top R_\delta (\mathbf{x}_i - \mathbf{x}_j)\right]$$

where $R_\delta = \text{diag}(\mathbf{r}_\delta)$ is a diagonal matrix of positive roughness parameters with $\mathbf{r}_\delta = [r_1^{(\delta)}, \dots, r_p^{(\delta)}] \in \mathbb{R}_+^p$, and the covariance matrix of the model outputs $\Sigma_\delta = \text{diag}(\sigma_\delta)$ is a diagonal matrix with positive variances $\sigma_\delta = [\sigma_1, \dots, \sigma_q] \in \mathbb{R}_+^q$.

The measurement error term $\epsilon(\cdot)$ is also modeled as a multivariate q -dimensional GP,

$$\epsilon(\cdot) \mid \boldsymbol{\psi} \sim \mathcal{GP}_q(\mathbf{0}, c_\epsilon(\cdot, \cdot) \Sigma_\epsilon) \quad (13)$$

with mean function equal to 0 for all elements, and correlation function given by the Kronecker delta function

$$c_\epsilon(\mathbf{x}_i, \mathbf{x}_j) = \begin{cases} 1 & \text{if } \mathbf{x}_i = \mathbf{x}_j \\ 0 & \text{if } \mathbf{x}_i \neq \mathbf{x}_j \end{cases}$$

and noise matrix $\Sigma_\epsilon = \text{diag}(\boldsymbol{\psi})$ with positive noise variances $\boldsymbol{\psi} = [\psi_1, \dots, \psi_q] \in \mathbb{R}_+^q$.

Notice that the model introduced in Equation (1) involves a summation of three random processes defined in Equations (7), (12) and (13). Here, we approximate

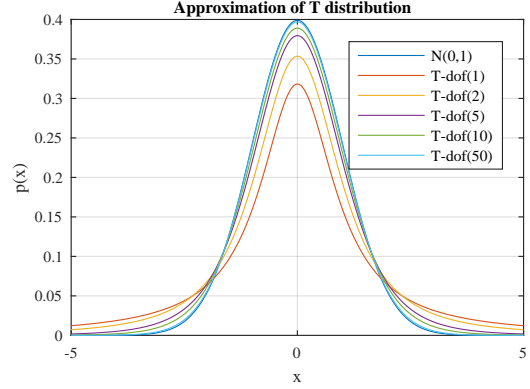


Figure 2: Approximation of T distributions to a normal distribution.

the multivariate T process (the surrogate model) with a Gaussian Process, so that the summation in the RHS of Equation (1) becomes another Gaussian Process due to the property of addition of statistically independent Gaussian random variables [63]. This approximation can be justified using an analogous case in a univariate setting. Figure 2 shows several univariate T distributions with different dof, in addition to a standard Normal distribution. It can be seen that as the value of dof increases (values larger than 10), the T distributions approximate perfectly to the standard Normal distribution. Therefore, if a T distribution is defined with dof equal to $N - m$ with $N > m$ for some $N \in \mathbb{N}$ and $m \in \mathbb{N}$, then a T distribution with relative large $N - m$ dof can be approximated with a Normal distribution. This is the case specially in our setting where the size of the training dataset for surrogate model N is relative larger than the dimension m from the mean function linear regression.

With this approximation, the calibration model resulting from Equation (1) is a multivariate q -dimensional GP given by

$$\mathbf{y}^E(\cdot) \mid \Phi_{\text{cal}} \sim \mathcal{GP}_q(m^*(\cdot, \theta), c^*(\cdot, \cdot) \hat{\Sigma} + c_\delta(\cdot, \cdot) \Sigma_\delta + c_\epsilon(\cdot, \cdot) \Sigma_\epsilon) \quad (14)$$

where $\Phi_{\text{cal}} = \{\theta, \mathbf{r}_\delta, \sigma_\delta, \boldsymbol{\psi}\}$ is the set of hyperparameters that will be estimated (including the calibration parameters θ).

In order to build the calibration model, we need another data set which is constructed from experimental observations. The procedure to obtain the experimental data is explained in Section 3.2. We denote this data set as

$$\mathbf{X}^E = \begin{bmatrix} \mathbf{x}_1^E \\ \vdots \\ \mathbf{x}_n^E \end{bmatrix} \in \mathbb{R}^{n,p} \quad \text{and} \quad \mathbf{Y}^E = \begin{bmatrix} \mathbf{y}^E(\mathbf{x}_1^E) \\ \vdots \\ \mathbf{y}^E(\mathbf{x}_n^E) \end{bmatrix} \in \mathbb{R}^{n,q}$$

where \mathbf{X}^E is an $n \times p$ controllable input matrix and $\mathbf{y}^E(\mathbf{x})$ is the result of the experiment observed at \mathbf{x} , thus \mathbf{Y}^E is a $n \times q$ matrix. It is worth to mention that the

size n of this dataset may be different from simulation dataset size N , and that only control inputs \mathbf{x} are used in the context of physical experiments (as opposed to $(\mathbf{x}, \boldsymbol{\theta})$ tuples for both the computer and surrogate models).

For implementation purposes, we rearrange the distribution resulting from Equation (14), by stacking each vector $\mathbf{y}^E(\mathbf{x}_i^E)$ and forming a single column vector with length $n \cdot q$, resulting in the following distribution,

$$p(\mathbf{Y}^E | \boldsymbol{\Phi}_{\text{cal}}, \mathbf{X}^E, \mathbf{X}^S, \mathbf{Y}^S) \sim \mathcal{MVN}_{n \cdot q}(\mathbf{m}^*, \boldsymbol{\Sigma}_{\text{cal}}) \quad (15)$$

with

$$\begin{aligned} \mathbf{Y}^E &= [Y_{1,1}^E, \dots, Y_{1,q}^E, \dots, Y_{n,1}^E, \dots, Y_{n,q}^E]^\top \in \mathbb{R}^{n \cdot q} \\ \mathbf{m}^* &= [m^*(\mathbf{x}_1^E, \boldsymbol{\theta}), \dots, m^*(\mathbf{x}_n^E, \boldsymbol{\theta})]^\top \in \mathbb{R}^{n \cdot q} \\ \boldsymbol{\Sigma}_{\text{cal}} &= \mathbf{C}_{\text{sur}}^{\text{cal}} \otimes \hat{\boldsymbol{\Sigma}} + \mathbf{C}_{\delta}^{\text{cal}} \otimes \boldsymbol{\Sigma}_{\delta} + \mathbf{C}_{\epsilon}^{\text{cal}} \otimes \boldsymbol{\Sigma}_{\epsilon} \in \mathbb{R}^{n \cdot q, n \cdot q} \\ \mathbf{C}_{\text{sur}}^{\text{cal}} &= [c^*((\mathbf{x}_i^E, \boldsymbol{\theta}), (\mathbf{x}_j^E, \boldsymbol{\theta}))]_{i,j=1:n} \in \mathbb{R}^{n,n} \\ \mathbf{C}_{\delta}^{\text{cal}} &= [c_{\delta}(\mathbf{x}_i^E, \mathbf{x}_j^E)]_{i,j=1:n} \in \mathbb{R}^{n,n} \\ \mathbf{C}_{\epsilon}^{\text{cal}} &= [c_{\epsilon}(\mathbf{x}_i^E, \mathbf{x}_j^E)]_{i,j=1:n} = \mathbf{I}_{n,n} \in \mathbb{R}^{n,n} \end{aligned}$$

where \otimes denotes the Kronecker matrix product employed to calculate cross-covariance matrix $\boldsymbol{\Sigma}_{\text{cal}}$ that accounts for the spatial dependence between inputs and outputs altogether.

The next step is to estimate the posterior distributions for the calibration parameters and hyperparameters. We conduct a Bayesian methodology to achieve this, where the posterior distributions of the hyperparameters $\boldsymbol{\Phi}_{\text{cal}}$ is given by

$$\boldsymbol{\theta}, \mathbf{r}_{\delta}, \boldsymbol{\sigma}_{\delta}, \boldsymbol{\psi} | \mathbf{X}^E, \mathbf{Y}^E, \mathbf{X}^S, \mathbf{Y}^S \propto p(\mathbf{Y}^E | \boldsymbol{\Phi}_{\text{cal}}, \mathbf{X}^E, \mathbf{X}^S, \mathbf{Y}^S) \pi(\boldsymbol{\theta}, \mathbf{r}_{\delta}, \boldsymbol{\sigma}_{\delta}, \boldsymbol{\psi})$$

The distributions are computed using the Metropolis Hastings algorithm after adequate selection of the prior distributions $\pi(\boldsymbol{\theta}, \mathbf{r}_{\delta}, \boldsymbol{\sigma}_{\delta}, \boldsymbol{\psi})$.

After determining these posterior distributions, the last remaining step is to construct a predictor that can be used to compute model predictions at input settings that have not been previously simulated or experimentally measured, and we rely on the *Kriging* technique, also known as the Best Linear Unbiased Estimator (BLUP) [64].

Let \mathbf{X}^{pred} denote a set of s control inputs $\mathbf{x}_i^{\text{pred}}$, that have not been previously simulated or experimentally measured

$$\mathbf{X}^{\text{pred}} = \begin{bmatrix} \mathbf{x}_1^{\text{pred}} \\ \vdots \\ \mathbf{x}_s^{\text{pred}} \end{bmatrix} \in \mathbb{R}^{s,p}$$

Then the predictive distribution of model outputs, $p(\mathbf{Y}_{\text{pred}}^E | \mathbf{X}^{\text{pred}}, \mathbf{X}^E, \mathbf{Y}^E, \mathbf{X}^S, \mathbf{Y}^S, \boldsymbol{\Phi}_{\text{cal}}, \boldsymbol{\Phi}_{\text{sim}})$, is an s -dimensional multivariate normal distribution with the following parameters:

- Expected value is given by:

$$\begin{aligned} \mathbb{E}[\mathbf{Y}_{\text{pred}}^E | \mathbf{X}^{\text{pred}}, \mathbf{X}^E, \mathbf{Y}^E, \mathbf{X}^S, \mathbf{Y}^S, \boldsymbol{\Phi}_{\text{cal}}, \boldsymbol{\Phi}_{\text{sim}}] \\ = \mathbf{m}_{\text{pred}}^* + \boldsymbol{\Sigma}_0 \boldsymbol{\Sigma}_{\text{cal}}^{-1} (\mathbf{Y}^E - \mathbf{m}^*) \end{aligned} \quad (16)$$

where

$$\begin{aligned} \mathbf{m}_{\text{pred}}^* &= [m^*(\mathbf{x}_1^{\text{pred}}, \boldsymbol{\theta}), \dots, m^*(\mathbf{x}_s^{\text{pred}}, \boldsymbol{\theta})]^\top \in \mathbb{R}^{s \cdot q} \\ \boldsymbol{\Sigma}_0 &= \mathbf{C}_{\text{sur}}^{\text{pred,cal}} \otimes \hat{\boldsymbol{\Sigma}} + \mathbf{C}_{\delta}^{\text{pred,cal}} \otimes \boldsymbol{\Sigma}_{\delta} \in \mathbb{R}^{s \cdot q, s \cdot q} \\ \mathbf{C}_{\text{sur}}^{\text{pred,cal}} &= [c^*((\mathbf{x}_i^{\text{pred}}, \boldsymbol{\theta}), (\mathbf{x}_j^E, \boldsymbol{\theta}))]_{i=1:s, j=1:n} \in \mathbb{R}^{s,n} \\ \mathbf{C}_{\delta}^{\text{pred,cal}} &= [c_{\delta}(\mathbf{x}_i^{\text{pred}}, \mathbf{x}_j^E)]_{i=1:s, j=1:n} \in \mathbb{R}^{s,n} \end{aligned}$$

- Variance is given by

$$\begin{aligned} \text{Var}[\mathbf{Y}_{\text{pred}}^E | \mathbf{X}^{\text{pred}}, \mathbf{X}^E, \mathbf{Y}^E, \mathbf{X}^S, \mathbf{Y}^S, \boldsymbol{\Phi}_{\text{cal}}, \boldsymbol{\Phi}_{\text{sim}}] \\ = \boldsymbol{\Sigma}_{\text{pred}} - \boldsymbol{\Sigma}_0 \boldsymbol{\Sigma}_{\text{cal}}^{-1} \boldsymbol{\Sigma}_0^\top, \end{aligned} \quad (17)$$

where

$$\begin{aligned} \boldsymbol{\Sigma}_{\text{pred}} &= \mathbf{C}_{\text{sur}}^{\text{pred}} \otimes \hat{\boldsymbol{\Sigma}} + \mathbf{C}_{\delta}^{\text{pred}} \otimes \boldsymbol{\Sigma}_{\delta} \\ &\quad + \mathbf{C}_{\epsilon}^{\text{pred}} \otimes \boldsymbol{\Sigma}_{\epsilon} \in \mathbb{R}^{s \cdot q, s \cdot q} \\ \mathbf{C}_{\text{sur}}^{\text{pred}} &= [c^*((\mathbf{x}_i^{\text{pred}}, \boldsymbol{\theta}), (\mathbf{x}_j^{\text{pred}}, \boldsymbol{\theta}))]_{i,j=1:s} \in \mathbb{R}^{s,s} \\ \mathbf{C}_{\delta}^{\text{pred}} &= [c_{\delta}(\mathbf{x}_i^{\text{pred}}, \mathbf{x}_j^{\text{pred}})]_{i,j=1:s} \in \mathbb{R}^{s,s} \\ \mathbf{C}_{\epsilon}^{\text{pred}} &= [c_{\epsilon}(\mathbf{x}_i^{\text{pred}}, \mathbf{x}_j^{\text{pred}})]_{i,j=1:s} \in \mathbb{R}^{s,s} \end{aligned}$$

To assess the performance of the calibrated model, a cross validation (CV) procedure similar to the one described for the surrogate model in Section 2.2.1 can be used. The mean absolute percentage error (MAPE) can be computed using Equations (16) and (17). The key difference is the fact that in this case, simulations from the calibrated surrogate model are compared with experimental measurements, in contrast to comparing surrogate model predictions with the computer model predictions.

3. Results: Calibration of FEM based thermal model using Ti-6Al-4V tracks

The statistical calibration procedure is conducted on the FEM based thermal model described in Section 2.1. Following our definitions, the thermal model represents the *computer model*, and the two terms will be used interchangeably in the remainder of the text. This computer model predicts the three-dimensional thermal profiles of the moving melt pool during L-PBF AM. It is reported in the literature that the melt pool temperature and geometry (depth and width) are important factors influencing the outcome of the L-PBF process [65]. The inputs and outputs of the computer model are described as follows:

- Two control inputs

- x_1 : laser power (W)
- x_2 : laser scan speed (mm/s)
- Three calibration parameters
 - θ_1 : powder-bed porosity (%)
 - θ_2 : laser absorptivity(%)
 - θ_3 : coefficient of thermal conductivity for liquid ($\frac{W}{m \cdot K}$)
- Three model outputs (or quantities of interest, QoIs)
 - y_1^S, y_1^E : melt pool depth into the solid substrate (μm)
 - y_2^S, y_2^E : melt pool width (μm)
 - y_3^S, y_3^E : melt pool peak temperature ($^{\circ}C$).

The chosen control inputs (laser power and speed) are known to have the most significant effect on the melt pool characteristics, and are commonly studied by AM researchers, see for example [64]. In terms of the notation defined in Section 2.2, we have the length of the control inputs vector $p = 2$, and lengths of the calibration parameters vector and computer model outputs vector $t = q = 3$. We test the performance of the proposed multivariate calibration procedure through studying the melt pool conditions while fabricating single track of Ti-6Al-4V. We derive the posterior distributions of the calibration parameters θ using a synthesis of computer model simulations denoted by matrices \mathbf{X}^S and \mathbf{Y}^S , and experimental observations denoted by matrices \mathbf{X}^E and \mathbf{Y}^E . We start by constructing a GP-based surrogate model using a data set of computer model simulations (Section 3.1). Next, we conduct manufacturing and characterization experiments to collect the data required for calibrating the model (Section 3.2). Finally, we conduct model calibration and prediction (see Section 3.3).

3.1. Building the surrogate model

Since L-PBF processes involve complicated physical phenomena with different forms of heat and mass transfer and material phase transitions, the run-times for computer simulation models are typically long. This necessitates the use of computationally efficient surrogate models, both for the purpose of conducting calibration or for process planning and optimization. In the present case, the execution time for the FEM based thermal model developed was dependent on the model inputs (control inputs and calibration parameters). From initial test simulation runs, execution times ranged between 30 minutes to 5 hours. Hence, performing a traditional Markov chain Monte Carlo (MCMC) with 50,000 iterations would take approximately 800 weeks. Furthermore, MCMC sampling strategies preclude the use of embarrassingly parallel modes of execution to improve computational time.

Instead, we use the two-stage surrogate-modeling approach explained in Section 2.2.1 to address this challenge.

To build the surrogate model, a training data set from the original FEM based thermal model is first needed. This data set consists of the two matrices \mathbf{X}^S and \mathbf{Y}^S introduced earlier, representing simulation inputs and outputs, respectively. We use the Latin Hypercube sampling (LHS) strategy to uniformly select design points from the control input and calibration parameters space, $\mathcal{X} \times \mathcal{T}$. The lower and upper bounds for the control input space \mathcal{X} was chosen as $\mathcal{X}_{min} = \{30 \text{ W}, 80 \text{ mm/s}\}$, and $\mathcal{X}_{max} = \{500 \text{ W}, 400 \text{ mm/s}\}$. These bounds were determined based on prior knowledge of the commercial metal L-PBF system used in this study and machine specifications. The lower and upper bounds for the calibration parameter space were chosen as $\mathcal{T}_{min} = \{20\%, 40\%, 1\}$, and $\mathcal{T}_{max} = \{70\%, 90\%, 25\}$. These bounds were specified by the AM researchers based on previous values reported in the literature to construct an initial region within which the true values of θ are believed to lie. A simulation data set of size $N = 130$ was generated over the $\mathcal{X} \times \mathcal{T}$ space. Hence, \mathbf{X}^S is an $N \times (p + t)$ matrix with 130 different and uniformly selected (\mathbf{x}, θ) combinations, and \mathbf{Y}^S is an $N \times q$ with elements representing outputs of the thermal model for input \mathbf{X}^S . Code parallelization was conducted on a 843-node high-performance super-computer.

Recall from Equation 7 that the conditional posterior distribution of $f(\cdot)$ given the simulation training data $(\mathbf{X}^S, \mathbf{Y}^S)$ and roughness parameters \mathbf{r} is a q -variate T Process. The Bayesian approach was then used to estimate the roughness parameters. To ensure their positivity, log-logistic prior distributions for the elements of \mathbf{r} with both scale and shape parameters equal to 1 were used (see Equation 11). Next, using the single-component Metropolis-Hastings algorithm, the posterior distributions of \mathbf{r} were generated after 50,000 iterations with 25% burn-in period and thinning every fifth sample. Figure 3 shows the histograms and kernel density estimates of the posterior distributions for the roughness parameters. The posteriors are very informative, and hence the modes were used as the estimates for the roughness parameters \mathbf{r} . At this stage, the surrogate model is built and ready to use, since essentially when the roughness parameters have been estimated, the output of the computer model at any given combination of (\mathbf{x}, θ) can be estimated using Equation 8. A confidence interval for this estimate can also be determined using Equation 9.

It is necessary to validate and assess the performance of the surrogate model once the hyperparameters Φ_{sim} are estimated. A 10-fold cross validation was performed for the surrogate model and the results are displayed in Figures 4a, 4b, and 4c, corresponding to the three model outputs: melt pool depth, width, and peak temperature, respectively. In the plots, the

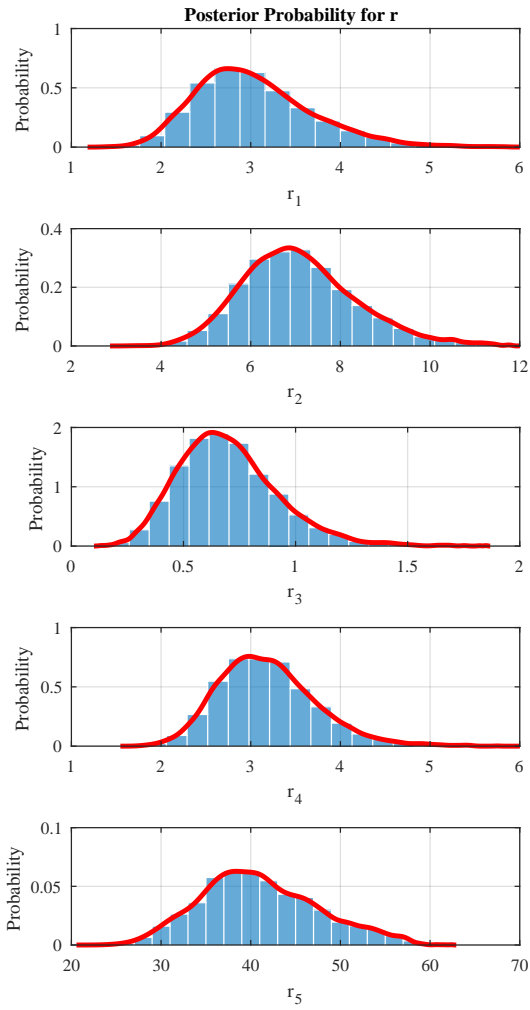


Figure 3: Histograms and kernel density estimates of the posterior distributions for the roughness parameters r for the surrogate model

horizontal axes represent the outputs of the computer simulation model, while the vertical axes show the predicted outputs using the surrogate model with the bars representing confidence intervals for these predictions. In other words, the red line represents the ideal case with surrogate model predictions $\mathbb{E}[f(\mathbf{x})|\mathbf{X}^S, \mathbf{Y}^S, \boldsymbol{\theta}]$ being in full agreement with computer model simulations $y^S(\mathbf{x}, \boldsymbol{\theta})$.

It can be visually seen that the predictive performance of the surrogate model is satisfactory. For a quantitative assessment, the computed MAPE values for the three outputs are reported in Table 1, also indicating satisfactory performance. Note that since the predictive accuracy, represented by MAPE, was deemed acceptable, there was no need for further sampling using the adaptive sampling technique described in Section 2.2.1.

3.2. Experimental measurements

As mentioned in Section 2.2, experimental data is needed to calibrate the computer model. LHS design was also used to uniformly explore the control input space \mathcal{X} . A total of $n = 24$ different configurations of \mathbf{x} were determined, which constitute \mathbf{X}^E . Next, the fabrication and characterization were conducted to obtain the corresponding outputs \mathbf{Y}^E .

3.2.1. Melt pool depth and width

Single tracks of length 20 mm were fabricated on a 30 μm powder-bed using a ProX 100 DMP commercial L-PBF system by 3D Systems. The system is equipped with a Gaussian profile fiber laser beam with wavelength $\lambda = 1070$ nm and beam spot size of approximately 70 μm -diameter. Argon was used as inert protective atmosphere during fabrication. The raw Ti-6Al-4V powder was produced by LPW Technology. Single tracks were built on a Ti-6Al-4V substrate, which was subsequently cut with a Buehler precision saw and mounted for cross-section analysis. Metallographic grinding was performed with silicon carbide papers (320 to 600 grit size) followed by manual polishing with 1 μm diamond suspension and final precision polishing with colloidal silica suspension. To make melt pool boundary lines more visible, chemical etching was performed using a 3:1 volume mixture of HCl and HNO_3 solution. Melt pool depth and width were measured using optical microscopy (Nikon Optiphot - POL) and verified with scanning electron microscopy (FEG-SEM/FIB TESCAN LYRA3). Representative SEM images that were used for measuring the melt pool depth and width are shown in Figure 5. We visually ascertain from the figure that both higher laser powers and lower scan speed increase the melt pool size; however, the impact of laser speed on the melt pool dimensions is higher, primarily due to the low maximum power on the system (50 W).

3.2.2. Melt pool peak temperature

The L-PBF system was custom integrated with a thermal imaging sensor to conduct in-situ monitoring of melt pool temperature during fabrication. The sensor is a two-wavelength imaging pyrometer (ThermaVIZ[®] by Stratronics Inc.) that consists of two high resolution CMOS imaging detectors. Both detectors have a field of view (FOV) with 1300 \times 1000 pixel resolution mapped to a 30 \times 27 mm area, which yields a resolution of 24 μm per pixel. Figure 6 shows the pyrometer integrated inside the ProX100 DMP build chamber. Experimental Calibration of the pyrometer (which is to be distinguished from statistical calibration of the model) was performed in-situ after integration using a tungsten filament (halogen tungsten-lamp) for a range of temperatures between 1500 – 2500 $^\circ\text{C}$. By fabricating the single tracks within the FOV of the pyrometer, thermal images of the melt pools were

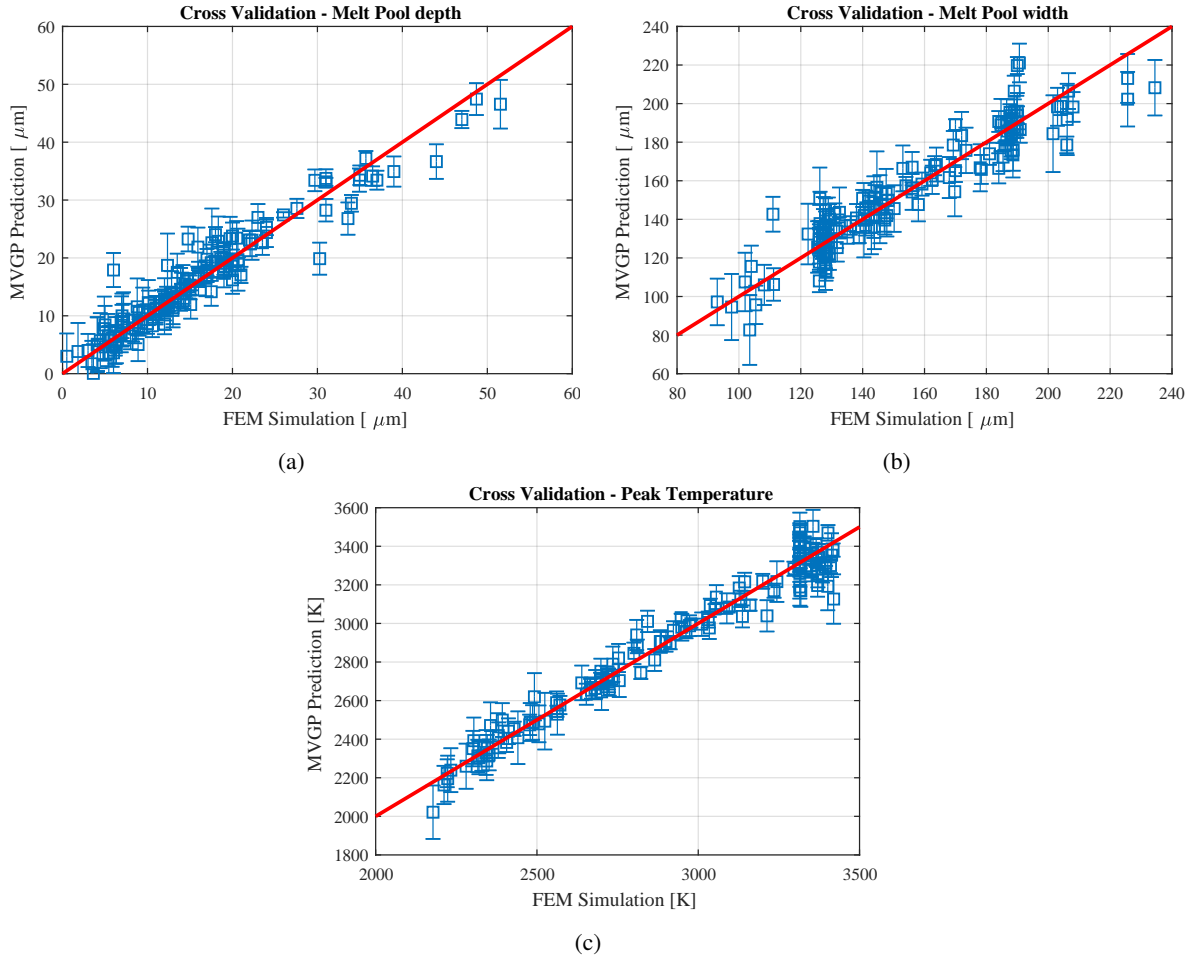


Figure 4: Results of a 10-fold cross validation of the surrogate model for (a) melt pool depth, (b) melt pool width, and (c) melt pool peak temperature

Table 1: Mean absolute predictive error (MAPE) of the surrogate model for the three outputs

Melt pool property	Depth	Width	Peak Temperature
Observed range in simulation	51.3 μm	147.8 μm	1284 K
Mean absolute predictive error (MAPE)	2.01 μm	8.05 μm	56.5 K
MAPE as % of the simulation range	4%	5%	4%

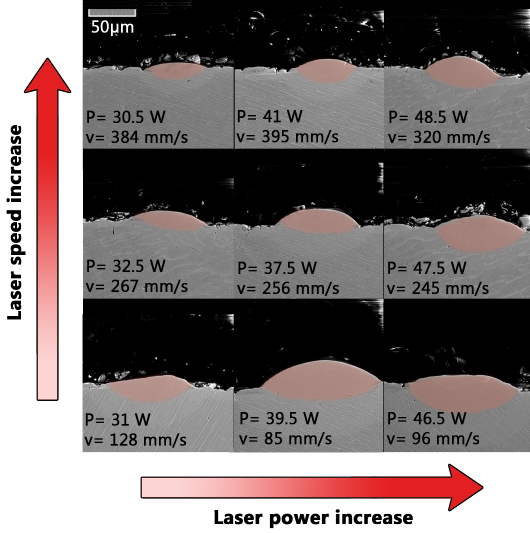


Figure 5: Representative SEM images used for measuring the melt pool depth and width

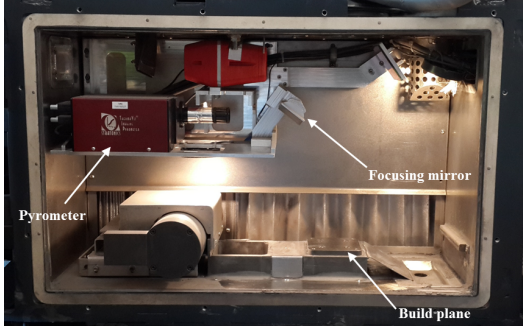


Figure 6: The two-wavelength pyrometer used for temperature measurement mounted inside the L-PBF machine

taken at approximately 250 Hz. These images were used to compute the melt pool peak temperature.

A sample melt pool temperature map taken from a representative thermal image is shown Figure 7 where X and Y coordinates are pixels resolved by the pyrometer and the color scale represents temperature. The temperature map shows zero for temperature values below 1500 °C that fall outside the calibration range of the pyrometer.

3.3. Prediction using the calibrated model

With the surrogate model fully defined and the experimental measurements conducted, we are now able to estimate the calibration parameters θ , as well as the remaining hyperparameters Φ_{cal} required for the statistical model (r_{δ} , σ_{δ} , and ψ , introduced in Equations 1, 12, and 13). As instructed in Section 2.2.2, we use the Bayesian framework and Metropolis-Hastings MCMC to estimate the set of hyperparameters $\Phi_{\text{cal}} = \{\theta, r_{\delta}, \sigma_{\delta}, \psi\}$. The following prior distributions are se-

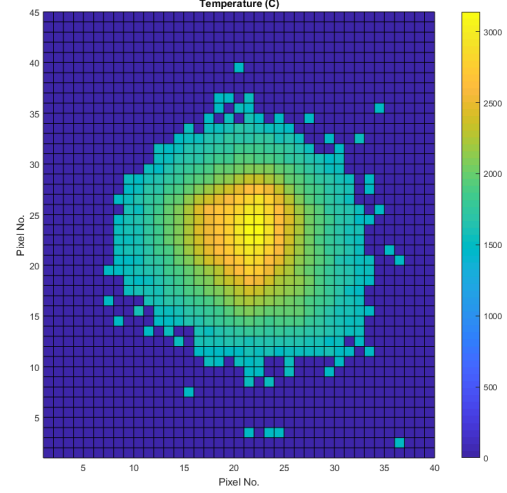


Figure 7: Temperature map of a sample melt pool captured using the pyrometer

lected for the hyperparameters:

$$\begin{aligned} \theta_i &\sim \text{Uniform}(\alpha_i^{\theta}, \beta_i^{\theta}) \\ r_{\delta_i} &\sim \text{Log-Logistic}(\alpha = 1, \beta = 1) \\ \sigma_i &\sim \text{Inverse-Gamma}(\alpha = 2, \beta = 1) \\ \psi_i &\sim \text{Inverse-Gamma}(\alpha = 2, \beta = 1) \end{aligned}$$

Note that the priors for the calibration parameters θ_i are all uniform and hence non-informative to avoid bias in estimation, and since no information beyond the suggested lower and upper bounds were available. Examples of constructing informative prior distributions using additional prior knowledge can be found in [66, 67]. The lower and upper bounds for these prior distributions, $(\alpha_i^{\theta}, \beta_i^{\theta})$, were set equal to the lower and upper bounds of the parameters space $\mathcal{T}_{\min} = \{20\%, 40\%, 1\}$, and $\mathcal{T}_{\max} = \{70\%, 90\%, 25\}$. For the roughness parameters r_{δ_i} , log-logistic priors were used as recommended by [59]. For the variance parameters σ_i and ψ_i , inverse gamma priors are selected because they represent conjugate priors for the multivariate normal likelihood function in our model.

Similar to Section 3.1, single-component Metropolis-Hastings procedure was used to compute the posterior distributions for the hyperparameters. Figure 8 shows the histograms and kernel density estimates for these parameters after 100,000 MCMC iterations with 25% burn-in period and thinning every fifth sample. In the plots, we observe unimodal and well-informative posteriors for all of the calibration parameters with θ_1 and θ_3 showing symmetric density functions and θ_2 showing a density function skewed to the right. Table 2 reports the posterior mean, mode, and standard deviation for the posterior distributions of the calibration parameters.

Porosity, θ_1 , is used to calculate the effective thermo-physical properties of the powder-bed (i.e., thermal conductivity and density). It was observed during simulations that by changing the porosity from

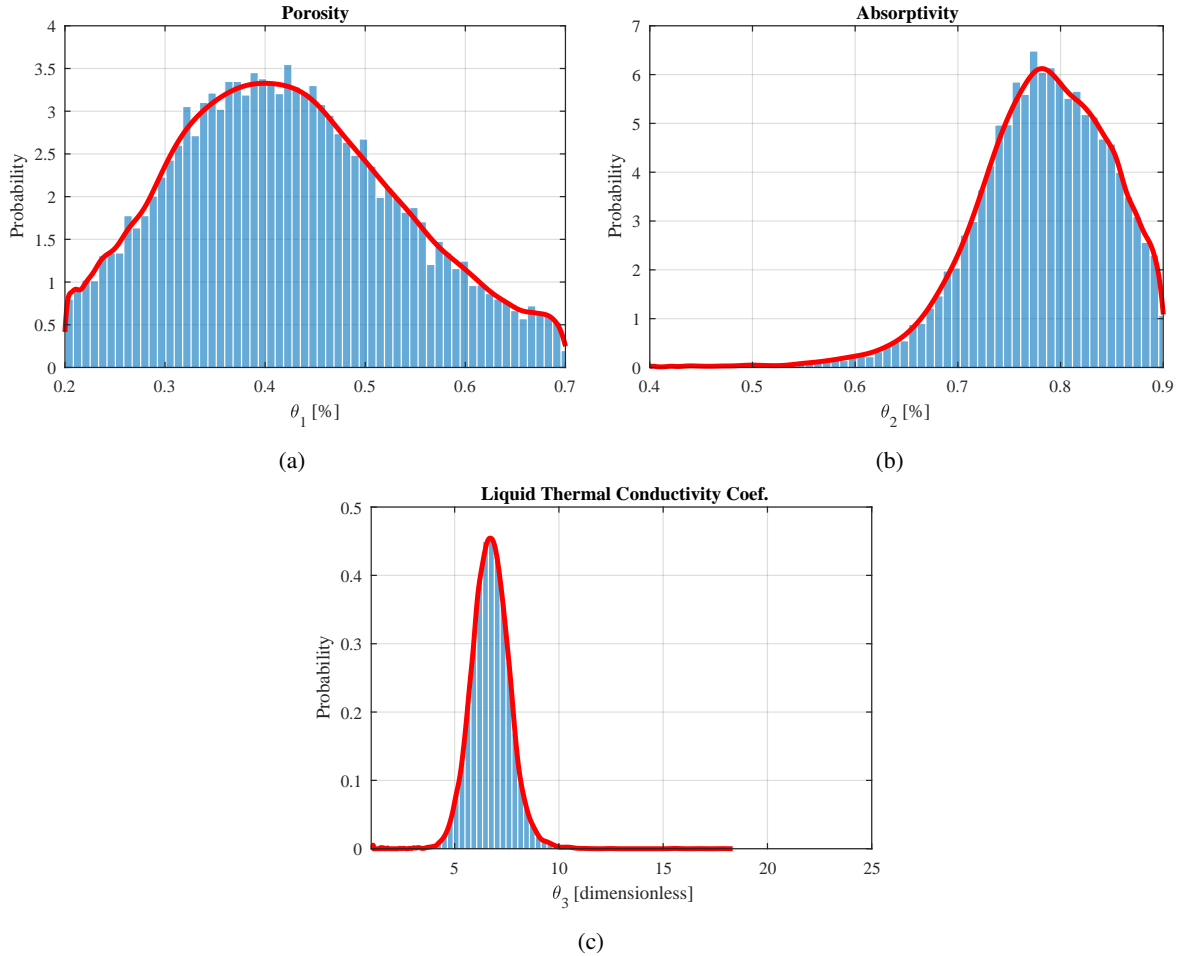


Figure 8: Histograms and kernel density estimates of the posterior distributions for calibration parameters (a) θ_1 : laser absorptivity, (b) θ_2 : powder-bed porosity, and (c) θ_3 : thermal conductivity of the liquid

Table 2: Posterior distribution parameters for the calibration parameters

Parameter	Posterior mean	Posterior mode	Posterior std. dev.
Powder porosity, θ_1	0.423	0.400	0.112
Laser absorptivity, θ_2	0.782	0.782	0.066
Coefficient of thermal conductivity for liquid, θ_3	6.727	6.709	0.922

0.3 to 0.5 the thermal conductivity of the powder changes up to $2 \frac{\text{W}}{\text{m}\cdot\text{K}}$, which leads to an insignificant change in the thermal history and only a few microns change in the melt pool size. Thus, by considering the variability in experimental measurements for melt pool dimensions, this change becomes negligible, and the wide nature of the posterior distribution for θ_1 is physically consistent. Furthermore, a posterior mean of 0.423 is reasonable since it agrees with the reported range of porosity for similar powder sizes and layer thicknesses, see [54, 68].

The posterior distribution of absorptivity (θ_2) shows a more informative posterior distribution with mean of 0.782. This value demonstrates reasonable agreement with reported experimental results in the literature [69, 70]. However, considering the difficulties

associated with experimentally measuring absorptivity due to its dependence on multiple parameters (i.e., wavelength, temperature, oxidation, powder size, powder distribution, powder porosity), these experimental results might involve high uncertainty. Therefore, we confidently agree that the estimated distribution for absorptivity is consistent with the underlying physical phenomena controlling the interactions between the laser and the powder bed.

The narrow range of the posterior distribution of θ_3 can be attributed to its significant effect on the thermal profile and the melt pool size. A unit increase in the liquid thermal conductivity coefficient might lead to a change on the order of 100 K in the thermal history and in a change between 5 to 10 μm in the melt pool size. Additionally, if extremely high values are

used for this parameter, the applied energy would be rapidly transferred to the surroundings and the energy input will reduce, thus the melt pool peak temperature would decrease in an unrealistic manner. Therefore, only a small region of this parameter results in physically meaningful simulations, explaining the narrow posterior distribution.

Next, we use the predictive distributions from Equation 16 to assess the performance of the calibrated model via a 6-fold cross validation. Figure 9 displays the results of the 6-fold cross validation for each of the three outputs y_i . In the plots, the horizontal axes represent experimental measurements, while the vertical axes are the predicted outputs using the calibrated model with the bars representing the confidence intervals for the predictions. In other words, each point on the plots compares the experiment $y^E(\mathbf{x}, \boldsymbol{\theta})$ versus the calibrated model prediction $\mathbb{E}[y^P(\mathbf{x})|X^E, Y^E, X^S, Y^S, \boldsymbol{\theta}^*]$, and the red straight line is a reference line representing ideal predictions.

Upon visual inspection, the plots qualitatively show acceptable predictive performance for y_1 (melt pool depth) and y_2 (melt pool width), but less accurate predictions for y_3 (peak temperature), particularly in the case with too low and too high values of y_3 . Quantitatively, the error metric MAPE for each output are reported in Table 3. We notice that the MAPEs for melt pool depth and width, y_1 and y_2 , are relatively low compared to the full range of simulations: 5% and 3%, respectively. These results show that the calibration model is effectively correcting the simulation model output when we use the Kriging technique in Equation 16. However, the predictions for melt pool peak temperature, y_3 , show a higher value of MAPE (12% of the simulation range) compared to the predictions for melt pool depth and width. We believe that this is due to the inherent high uncertainty associated with experimental temperature measurements using contactless temperature measurement through pyrometry [71]. The uncertainty in the temperature data can be measured by computing its standard deviation. The average standard deviation of the experimental measurements for y_1 , y_2 , and y_3 are $3.03 \mu\text{m}$, $8.14 \mu\text{m}$, and 306.3°C , respectively. We notice low standard deviations for y_1 and y_2 (6% of the simulation ranges), in contrast to a relatively high standard deviation for y_3 (24% of the simulation range). This is the likely explanation for the high MAPE associated with the predictions of y_3 due to high measurement noise, which signals the need for improving existing measurement techniques or developing new sensors with lower measurement noise.

To support our argument that uncertainty in experimental temperature measurements explain the high reported value of MAPE for y_3 , we re-implemented the multivariate calibration procedure with only the melt pool depth and width (y_1 and y_2 , respectively) as model outputs. In other words, we excluded the melt pool

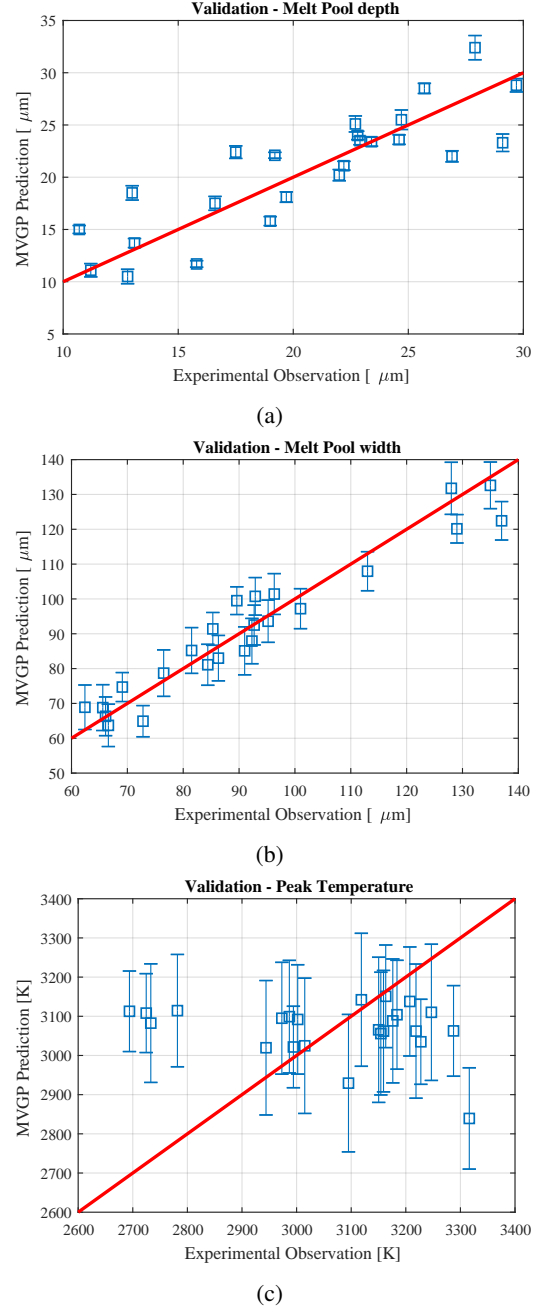


Figure 9: Results of the 6-fold cross validation for the predictions using the calibrated model for (a) y_1 : melt pool depth, (b) y_2 : melt pool width, and (c) y_3 : melt pool peak temperature

Table 3: Mean absolute predictive error (MAPE) of the predictions using the calibrated model

Melt pool property	Depth	Width	Peak Temperature
Mean absolute predictive error (MAPE)	2.42 μm	4.93 μm	159.5 K
MAPE as % of the experimental range	5%	3%	12%

temperature y_3 as a model output. Figure 10 shows the results of the 6-fold cross validation for this calibrated model. We observe that the cross validation plots show improvement in predictive performance, indicated by more proximity of the blue data points to the red line, narrower confidence intervals, and lower MAPE error values of 2.42 μm and 4.96 μm for y_1 and y_2 , respectively. This both supports our claim regarding measurement errors associated with temperature measurements, and also demonstrates satisfactory performance of the calibrated model.

4. Conclusions and future work directions

We developed an efficient procedure for conducting formal calibration (also known as inverse uncertainty quantification (UQ) analysis) of computational materials models. In addition to providing one of the first efforts to systematically perform UQ analysis for ICME models, we also present a versatile multivariate statistical framework to perform such analysis in the case of models with multiple quantities of interest (QoIs), in contrast to many previous research efforts that typically focus on a univariate scalar QoI. The proposed framework involves a two-step procedure that starts with constructing a computationally efficient multivariate Gaussian Process-based surrogate model that can be used in lieu of the original expensive computational model. The surrogate model can then be used to generate sufficiently large numbers of simulations needed to conduct calibration through a synthesis with experimental measurements.

We implemented the proposed multivariate statistical framework to calibrate a finite element method (FEM) based thermal model for laser powder-bed fusion metal additive manufacturing (L-PBF AM). The model predicts the thermal history and melt pool geometry during fabrication, and can potentially become one of the core elements of an ICME platform for the L-PBF process. Our results indicate that the multivariate surrogate model is capable of adequately approximating the original FEM based thermal model to a good degree of accuracy. Furthermore, predictions made using the calibrated model showed good agreement with experimental measurements conducted in a case study on fabricating single tracks of Ti-6Al-4V AM parts on a commercial L-PBF system instrumented with in-situ temperature monitoring capability.

The current work represents a foundation for numerous future investigations. First, coupling the calibrated melt pool model with other physics-based models in a

complete multi-model ICME platform for laser-based AM would be of great value. Second, calibration of ICME simulation models with high-dimensional output (e.g. fully explicit microstructure simulations) will be very useful but has not been conducted yet. Third, more validation experiments with other measurement instruments can be carried out to achieve better accuracy for predicting melt pool temperature.

Supplementary data

The complete dataset for building the surrogate model and calibrating the parameters as well as the MATLAB source codes have been shared and are freely available on github.com [72]. It includes the codes for loading the data, Monte Carlo simulation, and visualization of the outputs. The community can access and reproduce all of our results, in addition to use our models for their own data. Instructions regarding how to run the codes are given in the main scripts as identified on the Github repository.

Acknowledgement

This work was supported by an Early Stage Innovations grant from NASA’s Space Technology Research Grants Program, Grant No. NNX15AD71G. Portions of this research were conducted with High Performance Research Computing resources provided by Texas A&M University (<https://hprc.tamu.edu>). R. A. and LJ also acknowledge the support of NSF through the NSF Research Traineeship (NRT) program under Grant No. NSF-DGE-1545403, “NRT-DESE: Data-Enabled Discovery and Design of Energy Materials (D3EM).” R.A. and I.K. also acknowledge the partial support from NSF through Grant No. NSF-CMMI-1534534.

References

References

- [1] N. R. Council, et al., Integrated computational materials engineering: a transformational discipline for improved competitiveness and national security, National Academies Press, 2008.
- [2] A. O’Hagan, Bayesian analysis of computer code outputs: a tutorial, Reliability Engineering & System Safety 91 (2006) 1290–1300.
- [3] A. Chernatynskiy, S. R. Phillpot, R. LeSar, Uncertainty quantification in multiscale simulation of materials: A prospective, Annual Review of Materials Research 43 (2013) 157–182.

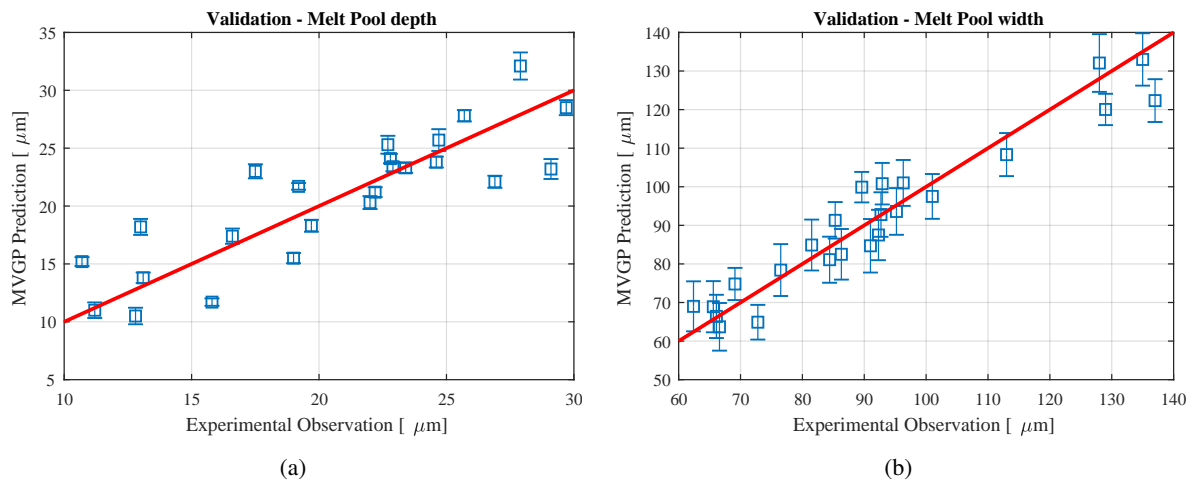


Figure 10: Results of the 6-fold cross validation for the predictions using the calibrated model with only two outputs (a) y_1 , (b) y_2

- [4] J. H. Panchal, S. R. Kalidindi, D. L. McDowell, Key computational modeling issues in integrated computational materials engineering, *Computer-Aided Design* 45 (2013) 4–25.
- [5] D. L. McDowell, S. R. Kalidindi, The materials innovation ecosystem: a key enabler for the materials genome initiative, *MRS Bulletin* 41 (2016) 326–337.
- [6] J. M. Murphy, D. M. Sexton, D. N. Barnett, G. S. Jones, et al., Quantification of modelling uncertainties in a large ensemble of climate change simulations, *Nature* 430 (2004) 768.
- [7] J. A. Witteveen, S. Sarkar, H. Bijl, Modeling physical uncertainties in dynamic stall induced fluid–structure interaction of turbine blades using arbitrary polynomial chaos, *Computers & structures* 85 (2007) 866–878.
- [8] M. Van Oijen, J. Rougier, R. Smith, Bayesian calibration of process-based forest models: bridging the gap between models and data, *Tree Physiology* 25 (2005) 915–927.
- [9] M. N. Avramova, K. N. Ivanov, Verification, validation and uncertainty quantification in multi-physics modeling for nuclear reactor design and safety analysis, *Progress in Nuclear Energy* 52 (2010) 601–614.
- [10] L. Kilian, T. Zha, Quantifying the uncertainty about the half-life of deviations from ppp, *Journal of Applied Econometrics* 17 (2002) 107–125.
- [11] M. A. Scales, A roadmapping study for connecting materials models and simulations across length and time scales (the minerals, metals and materials society, 2015), 2016.
- [12] D. Howe, B. Goodlet, J. Weaver, G. Spanos, Insights from the 3rd world congress on integrated computational materials engineering, *JOM* 68 (2016) 1378–1384.
- [13] G. Tapia, L. Johnson, B. Franco, K. Karayagiz, J. Ma, R. Arroyave, I. Karaman, A. Elwany, Bayesian calibration and uncertainty quantification for a physics-based precipitation model of nickel–titanium shape-memory alloys, *Journal of Manufacturing Science and Engineering* 139 (2017) 071002.
- [14] B. Franco, J. Ma, B. Loveall, G. Tapia, K. Karayagiz, J. Liu, A. Elwany, R. Arroyave, I. Karaman, A sensory material approach for reducing variability in additively manufactured metal parts, *Scientific Reports* 7 (2017).
- [15] A. Bauereiß, T. Scharowsky, C. Körner, Defect generation and propagation mechanism during additive manufacturing by selective beam melting, *Journal of Materials Processing Technology* 214 (2014) 2522–2528.
- [16] F. Lopez, P. Witherell, B. Lane, Identifying uncertainty in laser powder bed fusion additive manufacturing models, *Journal of Mechanical Design* 138 (2016) 114502.
- [17] M. Seifi, A. Salem, J. Beuth, O. Harrysson, J. J. Lewandowski, Overview of materials qualification needs for metal additive manufacturing, *JoM* 68 (2016) 747–764.
- [18] Z. Hu, S. Mahadevan, Uncertainty quantification in prediction of material properties during additive manufacturing, *Scripta Materialia* 135 (2017) 135–140.
- [19] Z. Hu, S. Mahadevan, Uncertainty quantification and management in additive manufacturing: current status, needs, and opportunities, *The International Journal of Advanced Manufacturing Technology* (2017) 1–20.
- [20] T. G. Trucano, L. P. Swiler, T. Igusa, W. L. Oberkampf, M. Pilch, Calibration, validation, and sensitivity analysis: What’s what, *Reliability Engineering & System Safety* 91 (2006) 1331–1357.
- [21] B. Liu, Q. Xu, Advances on microstructure modeling of solidification process of shape casting, *Tsinghua Science and Technology* 9 (2004) 497–505.
- [22] P. Liu, M. T. Lusk, Parametric links among monte carlo, phase-field, and sharp-interface models of interfacial motion, *Physical Review E* 66 (2002) 061603.
- [23] E. Holm, D. J. Srolovitz, J. Cahn, Microstructural evolution in two-dimensional two-phase polycrystals, *Acta metallurgica et materialia* 41 (1993) 1119–1136.
- [24] J. Spittle, S. Brown, Computer simulation of the effects of alloy variables on the grain structures of castings, *Acta Metallurgica* 37 (1989) 1803–1810.
- [25] P. Zhu, R. Smith, Dynamic simulation of crystal growth by monte carlo method i. model description and kinetics, *Acta metallurgica et materialia* 40 (1992) 683–692.
- [26] D. Higdon, J. Gattiker, B. Williams, M. Rightley, Computer model calibration using high-dimensional output, *Journal of the American Statistical Association* 103 (2008) 570–583.
- [27] R. Paulo, G. García-Donato, J. Palomo, Calibration of computer models with multivariate output, *Computational Statistics & Data Analysis* 56 (2012) 3959–3974.
- [28] S. A. Khairallah, A. T. Anderson, A. Rubenchik, W. E. King, Laser powder-bed fusion additive manufacturing: Physics of complex melt flow and formation mechanisms of pores, spatter, and denudation zones, *Acta Materialia* 108 (2016) 36–45.
- [29] S. A. Khairallah, A. Anderson, Mesoscopic simulation model of selective laser melting of stainless steel powder, *Journal of Materials Processing Technology* 214 (2014) 2627–2636.
- [30] R. Ganeriwala, T. I. Zohdi, A coupled discrete element-finite difference model of selective laser sintering, *Granular Matter* 18 (2016) 21.
- [31] C. Qiu, C. Panwisawas, M. Ward, H. C. Basoalto, J. W. Brooks, M. M. Attallah, On the role of melt flow into the surface structure and porosity development during selective laser melting, *Acta Materialia* 96 (2015) 72–79.
- [32] K. Leitz, P. Singer, A. Plankensteiner, B. Tabernig, H. Kestler, L. Sigl, Multi-physical simulation of selective laser melting of molybdenum, *Proceedings of Euro PM* (2015) 4–7.
- [33] C. Panwisawas, C. Qiu, M. J. Anderson, Y. Sovani, R. P. Turner, M. M. Attallah, J. W. Brooks, H. C. Basoalto, Mesoscale modelling of selective laser melting: Thermal fluid

- dynamics and microstructural evolution, *Computational Materials Science* 126 (2017) 479–490.
- [34] S. Ly, A. M. Rubenchik, S. A. Khairallah, G. Guss, M. J. Matthews, Metal vapor micro-jet controls material redistribution in laser powder bed fusion additive manufacturing, *Scientific Reports* 7 (2017).
- [35] W. Pei, W. Zhengying, C. Zhen, L. Junfeng, Z. Shuzhe, D. Jun, Numerical simulation and parametric analysis of selective laser melting process of alsi10mg powder, *Applied Physics A* 123 (2017) 540.
- [36] M. Matsumoto, M. Shiomi, K. Osakada, F. Abe, Finite element analysis of single layer forming on metallic powder bed in rapid prototyping by selective laser processing, *International Journal of Machine Tools and Manufacture* 42 (2002) 61–67.
- [37] I. A. Roberts, C. Wang, R. Esterlein, M. Stanford, D. Mynors, A three-dimensional finite element analysis of the temperature field during laser melting of metal powders in additive layer manufacturing, *International Journal of Machine Tools and Manufacture* 49 (2009) 916–923.
- [38] F. Verhaeghe, T. Craeghs, J. Heulens, L. Pandelaers, A pragmatic model for selective laser melting with evaporation, *Acta Materialia* 57 (2009) 6006–6012.
- [39] N. Shen, K. Chou, Thermal modeling of electron beam additive manufacturing process. powder sintering effects, *ASME Paper No. MSEC2012-7253* (2012).
- [40] A. Hussein, L. Hao, C. Yan, R. Everson, Finite element simulation of the temperature and stress fields in single layers built without-support in selective laser melting, *Materials & Design* 52 (2013) 638–647.
- [41] C. Fu, Y. Guo, 3-dimensional finite element modeling of selective laser melting ti-6al-4v alloy, in: *25th Annual International Solid Freeform Fabrication Symposium*, 2014.
- [42] L.-E. Loh, C.-K. Chua, W.-Y. Yeong, J. Song, M. Mapar, S.-L. Sing, Z.-H. Liu, D.-Q. Zhang, Numerical investigation and an effective modelling on the selective laser melting (slm) process with aluminium alloy 6061, *International Journal of Heat and Mass Transfer* 80 (2015) 288–300.
- [43] J. Romano, L. Ladani, M. Sadowski, Thermal modeling of laser based additive manufacturing processes within common materials, *Procedia Manufacturing* 1 (2015) 238–250.
- [44] T. Heeling, M. Cloots, K. Wegener, Melt pool simulation for the evaluation of process parameters in selective laser melting, *Additive Manufacturing* 14 (2017) 116–125.
- [45] M. Xia, D. Gu, G. Yu, D. Dai, H. Chen, Q. Shi, Porosity evolution and its thermodynamic mechanism of randomly packed powder-bed during selective laser melting of inconel 718 alloy, *International Journal of Machine Tools and Manufacture* 116 (2017) 96–106.
- [46] Y. Huang, L. Yang, X. Du, Y. Yang, Finite element analysis of thermal behavior of metal powder during selective laser melting, *International Journal of Thermal Sciences* 104 (2016) 146–157.
- [47] K. Dai, L. Shaw, Thermal and stress modeling of multi-material laser processing, *Acta Materialia* 49 (2001) 4171–4181.
- [48] L. Van Belle, G. Vansteenkiste, J. C. Boyer, Comparisons of numerical modelling of the selective laser melting, in: *Key Engineering Materials*, volume 504, *Trans Tech Publ*, 2012, pp. 1067–1072.
- [49] Y. Liu, J. Zhang, Z. Pang, Numerical and experimental investigation into the subsequent thermal cycling during selective laser melting of multi-layer 316l stainless steel, *Optics & Laser Technology* 98 (2018) 23–32.
- [50] K. Zeng, D. Pal, B. Stucker, A review of thermal analysis methods in laser sintering and selective laser melting, in: *Proceedings of Solid Freeform Fabrication Symposium Austin, TX, 2012*, pp. 796–814.
- [51] B. Schoinochoritis, D. Chantzis, K. Salonitis, Simulation of metallic powder bed additive manufacturing processes with the finite element method: A critical review, *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture* 231 (2017) 96–117.
- [52] M. Markl, C. Körner, Multiscale modeling of powder bed-based additive manufacturing, *Annual Review of Materials Research* 46 (2016) 93–123.
- [53] G. Vastola, G. Zhang, Q. Pei, Y.-W. Zhang, Modeling the microstructure evolution during additive manufacturing of ti6al4v: a comparison between electron beam melting and selective laser melting, *JOM* 68 (2016) 1370–1375.
- [54] B. Cheng, S. Price, J. Lydon, K. Cooper, K. Chou, On process temperature in powder-bed electron beam additive manufacturing: Model development and validation, *Journal of Manufacturing Science and Engineering* 136 (2014) 061018.
- [55] M. C. Kennedy, A. O’Hagan, Bayesian calibration of computer models, *Journal of the Royal Statistical Society. Series B, Statistical Methodology* (2001) 425–464.
- [56] J. Sacks, W. J. Welch, T. J. Mitchell, H. P. Wynn, Design and analysis of computer experiments, *Statistical science* (1989) 409–423.
- [57] R. Haylock, A. O’Hagan, On inference for outputs of computationally expensive algorithms with uncertainty on the inputs, *Bayesian statistics* 5 (1996) 629–637.
- [58] J. Oakley, A. O’Hagan, Bayesian inference for the uncertainty distribution of computer model outputs, *Biometrika* 89 (2002) 769–784.
- [59] S. Conti, A. O’Hagan, Bayesian emulation of complex multi-output and dynamic computer models, *Journal of statistical planning and inference* 140 (2010) 640–651.
- [60] C. E. Rasmussen, C. K. I. Williams, *Gaussian Processes for Machine Learning*, The MIT Press, Cambridge, MA, 2006.
- [61] A. E. Gelfand, P. Diggle, P. Guttorp, M. Fuentes, *Handbook of Spatial Statistics*, CRC Press, Boca Raton, FL, 2010.
- [62] K. Bhat, M. Haran, M. Goes, Computer model calibration with multivariate spatial output: A case study, *Frontiers of Statistical Decision Making and Bayesian Analysis* (2010) 168–184.
- [63] G. Casella, R. L. Berger, *Statistical inference*, volume 2, Duxbury Pacific Grove, CA, 2002.
- [64] G. Tapia, S. Khairallah, M. Matthews, W. E. King, A. Elwany, Gaussian process-based surrogate modeling framework for process planning in laser powder-bed fusion additive manufacturing of 316l stainless steel, *The International Journal of Advanced Manufacturing Technology* (2017) 1–13.
- [65] M. Mani, S. Feng, B. Lane, A. Donmez, S. Moylan, R. Fesperman, Measurement science needs for real-time control of additive manufacturing powder bed fusion processes, *US Department of Commerce, National Institute of Standards and Technology*, 2015.
- [66] S. Boluki, M. S. Esfahani, X. Qian, E. R. Dougherty, Incorporating biological prior knowledge for bayesian learning via maximal knowledge-driven information priors, *BMC Bioinformatics* 18 (2017) 1–1.
- [67] S. Boluki, M. S. Esfahani, X. Qian, E. R. Dougherty, Constructing pathway-based priors within a gaussian mixture model for bayesian regression and classification, *IEEE/ACM Transactions on Computational Biology and Bioinformatics PP* (2017) 1–1.
- [68] J. Romano, L. Ladani, M. Sadowski, Laser additive melting and solidification of inconel 718: finite element simulation and experiment, *Jom* 68 (2016) 967–977.
- [69] C. Boley, S. Khairallah, A. Rubenchik, Calculation of laser absorption by metal powders in additive manufacturing, *Applied optics* 54 (2015) 2477–2482.
- [70] A. Rubenchik, S. Wu, S. Mitchell, I. Golosker, M. LeBlanc, N. Peterson, Direct measurements of temperature-dependent laser absorptivity of metal powders, *Applied optics* 54 (2015) 7230–7233.
- [71] M. Grasso, B. M. Colosimo, Process defects and in situ monitoring methods in metal powder bed fusion: a review, *Measurement Science and Technology* 28 (2017) 044005.
- [72] M. Mahmoudi, G. Tapia, *Multivariate statistical calibration of computer simulation models*, 2017. URL: <https://github.com/mahmoudi-tapia/MVcalibration>.